



This MotoCAP safety rating applies to:

Brand: BMW
Model: Tourshell

Type: Jacket - Textile

Date purchased: 11 February 2019

Sizes tested:52 and 54Gender:M & FStyle:TourerTest code:J19T03


Test Results Summary:

	Rating	Score
MotoCAP Protection Rating	**	39.2
Abrasion	1/10	0.28
Burst	10/10	1570
Impact	9/10	73.5
MotoCAP Comfort Rating	*	0.173
Moisture Vapour Resistance		108.1
Thermal Resistance		0.312
Water resistance	5/10	10.3

This garment is fitted with impact protectors for the elbows, shoulders and back. Vents are provided on each side of the front and back to allow airflow cooling in hot weather. The thermal comfort measurements undertaken have not evaluated the performance of venting provided in this garment. The thermal comfort of this product may be better in dry weather when the vents can be opened.

Jacket and Pants - Crash Impact Risk Zones

This diagram is a pictorial representation of the crash impact risk Zones.

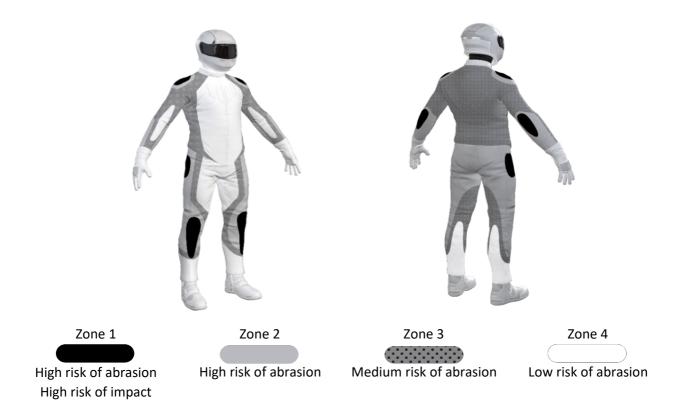



Abrasion Resistance

The garment was tested for abrasion resistance in accordance with MotoCAP test protocols. The table below shows the test results for time to abrade through all layers of the materials. Calculated for each sample by Zone, type and area coverage of each material as a proportion of that Zone.

Details of materials used in garment:


Material A: Woven fabric shell, water resistant layer, foam layer and mesh inner liner

Material B: Woven fabric shell, water resistant layer and mesh inner liner

Zone	Coverage	Abrasion t	Average					
	(%)	1	2	3	4	5	6	(seconds)
Zone 1 and 2	areas (High abra	asion risk)						
Material A	50%	2.28	1.82	3.74	2.80	4.16	3.82	3.10 A
Material B	50%	0.64	0.54	0.56	0.58	0.94	0.67	0.66 P
Zone 3 area (l	Medium abrasioi	n risk)						
Material A	20%	2.28	1.82	3.74	2.80	4.16	3.82	3.10 G
Material B	80%	0.64	0.54	0.56	0.58	0.94	0.67	0.66 P
Zone 4 area (l	Low abrasion ris	sk)						
Material B	100%	0.64	0.54	0.56	0.58	0.94	0.67	0.66 M

Abrasion times are capped at a maximum of 10.00s.

The diagram below is a visual indication of the likely abrasion performance of the materials in each zone calculated from the data in the table above. The colour coding is based on the worst performing material in each zone.

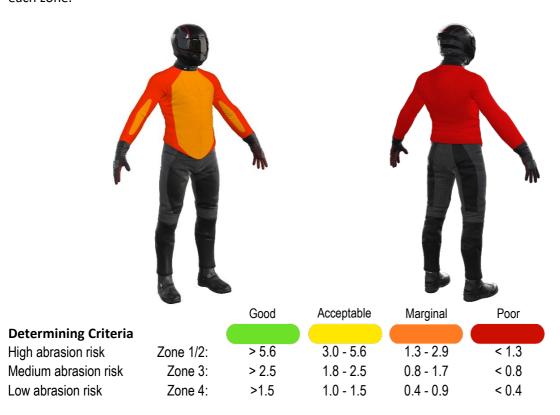




Burst Strength

The garment's burst strength was tested in accordance with MotoCAP test protocols. The table below shows the burst pressure in kilopascals (kPA) for each sample tested by Zone and the average result for each zone.

Burst pressure (kPA)

Area	1	2	3	4	5	Average
Zones 1 & 2	1844	1930	1198	1877	1932	1757 G
Zone EZ	1938	1663	1246	1254	1132	1446 G
Zones 3 & 4	1211	1172	1475	1490	1865	1443 G

The diagram below illustrates the burst strength results in terms of the likely performance of the garment in an impact and is a pictorial representation of the data from the table above.

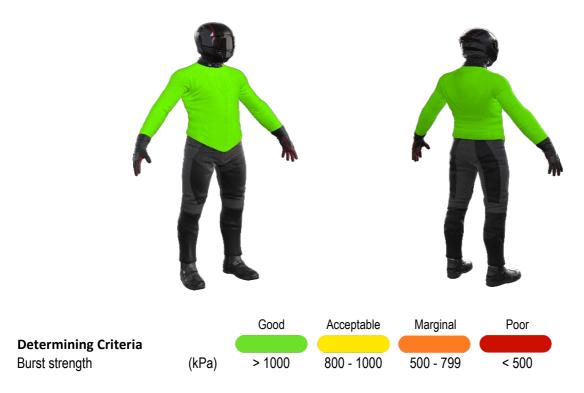

motocap.com.au



Impact Protection


The garment was tested for impact protection and coverage in accordance with MotoCAP test protocols. The table below shows the test results for each strike on each impact protector in kilonewtons (kN) and their area of coverage as a proportion (%) of the Zone.

Impact protector type	Elbow		Shoulder
Average force (kN)	10.8	G	13.9 G
Maximum force (kN)	18.2	A	16.7 A
Coverage of zone 1 area	150%		120%
Coverage of zone after displacement	100%		100%

Individual test results

Impact force (kN)	Elbow			Shoulder		
Strike location	Α	В	С	Α	В	С
Impact Protector 1	6.6	7.9	18.2	12.4	14.2	15.7
Impact Protector 2	7.4	14.7	9.2	11.8	12.9	16.7
Impact Protector 3	7.2	8.8	17.5	12.4	13.6	15.6

The diagram below is a visual indication of the likely performance of each impact protector calculated from the data in the table above. The colour coding is based on the worst performing score for average or maximium force for each impact zone.

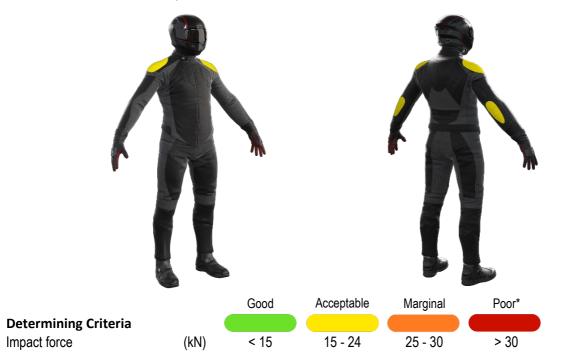

^{*} Poor may also indicate that no impact protector, or impact protector pocket is present in the garment

Areas shaded black are not considered in the impact protection ratings.



Thermal comfort

The garment was tested for thermal comfort following the MotoCAP test protocols. The table below shows the moisture vapour resistance and the thermal resistance values obtained.

	1	2	Average
Moisture Vapour Resistance - Ret	113.1	103.2	108.1
(kPam²/W)			
	1	2	Average
Thermal Resistance - R _{ct}	0.322	0.301	0.312
(Km²/W)			

Water spray and rain resistance

This garment is advertised as water-resistant, and so has been tested for water spray and rain resistance according to the MotoCAP test protocols. The table below shows the increased weight (g) and proportion (%) of the garment and undergarments due to water absorption.

	Water absorbe	ed by garment	Water absorbed by underwear		
	Volume (ml)	Percentage (%)	Volume (ml)	Percentage (%)	
Garment 1	407	22%	29.8	11%	
Garment 2	359	19%	27.0	10%	
Average	255	21%	18.9	10%	

Location of wetting:

Minor visible wetting to the cotton undergarment worn under the motorcycle water resistant jacket was present on the neck, chest and cuffs of the sleeves.