


**This MotoCAP safety rating applies to:**

Brand	PANDO MOTO
Model	SKIN UH AAA
Type	Pants(Undergarment) -Textile
Date purchased	4 December 2024
Sizes tested	XL and XXL
Test garment gender	Male and Female
Style	All Purpose
RRP	\$539.00

Test Results Summary	Rating	Score
MotoCAP Protection Rating	★★★★	52.8
Abrasion	9/10	6.62
Burst	5/10	597
Impact	6/10	45.7
MotoCAP Breathability Rating	★★	0.361
Moisture Vapour Resistance	-	19.1
Thermal Resistance	-	0.115
Water resistance	N/A	N/A

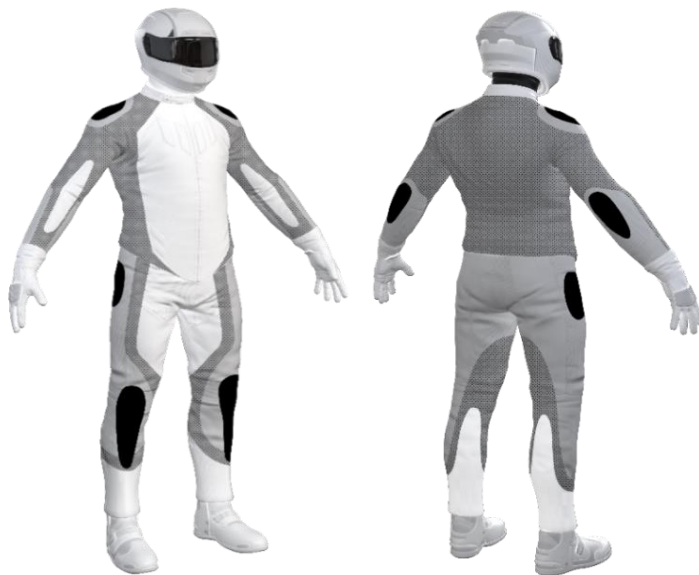
This garment is an undergarment designed to be worn under denim pants.

This garment is fitted with impact protectors for the knees and hips. There are no vents to allow airflow movement through the garment.

The abrasion test results above were conducted under a 10 ounce denim. Protection levels may be lower if this garment was worn under different pant materials. The garment scored 6/10 (4.87) for abrasion and three stars (44.0) for protection when tested as a stand-alone garment.

**Jacket and Pants - Crash Impact Risk Zones**

This diagram is a pictorial representation of the crash impact risk Zones.


**Zone 1**

High risk of abrasion  
High risk of impact

**Zone 2**

High risk of abrasion

**Zone 3**

Medium risk of abrasion

**Zone 4**

Low risk of abrasion

**Removable liners**

Thermal liner

Water-resistant liner


**Removable impact protection**

Knee  
Hip

Pockets

Armour



## Abrasion Resistance

These pants were tested for abrasion resistance in accordance with MotoCAP test protocols. The diagram below is a visual indication of the likely abrasion performance of the materials in each zone calculated from the data in the table below. The colour coding is based on the worst performing material in each zone.



### Abrasion Resistance Performance

Abrasion rating	9/10
Abrasion score	6.62

Determining Criteria	Area	Good	Acceptable	Marginal	Poor
High abrasion risk	Zones 1 & 2	> 5.6	3.0 - 5.6	1.3 - 2.9	< 1.3
Medium abrasion risk	Zone 3	> 2.5	1.8 - 2.5	0.8 - 1.7	< 0.8
Low abrasion risk	Zone 4	> 1.5	1.0 - 1.5	0.4 - 0.9	< 0.4

**Individual Abrasion Resistance Results:** - The table below shows the test results for time to abrade through all layers of the materials. Calculated for each sample by Zone, type and area coverage of each material as a proportion of that Zone. Abrasion times are capped at a maximum of 10.00s.

### Abrasion time for each test (seconds)

Zones 1 & 2	Coverage (%)	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average	
Material A	100%	9.22	8.01	8.18	8.47	8.38	10.00	8.71	<div style="background-color: #90EE90; border: 1px solid black; width: 20px; height: 20px; display: inline-block;"></div>
<b>Zone 3</b>	<b>Coverage (%)</b>	<b>Sample 1</b>	<b>Sample 2</b>	<b>Sample 3</b>	<b>Sample 4</b>	<b>Sample 5</b>	<b>Sample 6</b>	<b>Average</b>	
Material A	30%	9.22	8.01	8.18	8.47	8.38	10.00	8.71	<div style="background-color: #90EE90; border: 1px solid black; width: 20px; height: 20px; display: inline-block;"></div>
Material C	70%	2.03	3.00	2.06	2.10	2.07	1.85	2.19	<div style="background-color: #FFFF00; border: 1px solid black; width: 20px; height: 20px; display: inline-block;"></div>
<b>Zone 4</b>	<b>Coverage (%)</b>	<b>Sample 1</b>	<b>Sample 2</b>	<b>Sample 3</b>	<b>Sample 4</b>	<b>Sample 5</b>	<b>Sample 6</b>	<b>Average</b>	
Material B	20%	3.65	3.49	3.09	3.84	3.69	2.26	3.34	<div style="background-color: #90EE90; border: 1px solid black; width: 20px; height: 20px; display: inline-block;"></div>
Material C	80%	2.03	3.00	2.06	2.10	2.07	1.85	2.19	<div style="background-color: #90EE90; border: 1px solid black; width: 20px; height: 20px; display: inline-block;"></div>

### Details of materials used in pant

Material A	Denim fabric shell with double layers of thick stretch fabric
Material B	Denim fabric shell with thick stretch fabric layer
Material C	Denim fabric shell with stretch fabric layer

## Burst Strength

These pants were tested for burst strength in accordance with MotoCAP test protocols. The diagram below illustrates the burst strength results in terms of the likely performance of the garment in an impact and is a pictorial representation of the data from the table below.



### Burst Strength Performance

Burst rating	5/10
Burst score	597

Determining Criteria	Unit	Good	Acceptable	Marginal	Poor
Burst strength	(kPa)	> 1000	800 - 1000	500 - 799	< 500

**Individual Burst Strength Results:** - The table below shows the burst pressure in kilopascals (kPa) for each sample tested by Zone and the average result for each zone.

### Burst pressure for each seam (kPa)

Area	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average	
Zones 1 & 2	685	853	877	438	376	555	631	M
Zones 3 & 4	446	469	508	439	443		461	P

## Impact Protection

These pants were tested for impact protection and coverage in accordance with MotoCAP test protocols. The diagram below is a visual indication of the likely performance of each impact protector calculated from the data in the table below. The colour coding is based on the worst performing score for average or maximum force for each impact zone. Areas shaded black are not considered for impact protection ratings.



### Impact Protection Performance

Impact rating	6/10
Impact score	45.7

Determining Criteria	Unit	Good	Acceptable	Marginal	Poor*
Impact force	(kN)	< 15	15 - 24	25 - 30	> 30

\* Poor may also indicate that no impact protector, or impact protector pocket is present in the garment

**Impact Protector Results:** - The table below shows the average and maximum force transmitted through each impact protector type in kilonewtons (kN) and their area of coverage as a proportion (%) of the Zone.

Impact protector type	Knee		Hip	
Average force (kN)	19.0	A	21.7	A
Maximum force (kN)	20.6	A	24.3	A
Coverage of Zone 1 area	85%		150%	
Coverage of Zone after displacement	85%		100%	

**Individual Impact Protector Results:** - The table below shows the test results for each strike on individual impact protectors in kilonewtons (kN) and the position of the strike. Individual strike results are capped at a maximum of 50kN.

### Force transfer for each impact strike (kN)

Impact protector type	Knee			Hip		
	Centre	Mid	Edge	Centre	Mid	Edge
Impact Protector 1	16.0	19.3	20.4	19.8	20.1	22.7
Impact Protector 2	19.5	19.6	18.7	21.4	24.3	22.7
Impact Protector 3	19.4	20.6	17.8	21.5	20.2	22.4

### Breathability

These pants were tested for breathability following the MotoCAP test protocols. The table below shows the moisture vapour resistance and the thermal resistance values obtained.

Without removable liners		With water-resistant liner	
Breathability rating	★★	Breathability rating	N/A
Breathability score	0.361	Breathability score	N/A

Moisture Vapour Resistance - $R_{et}$ (kPa.m <sup>2</sup> /W)	1	2	Average
Without removable liners	18.3	19.9	19.1
With water-resistant liner	N/A	N/A	N/A

Thermal Resistance - $R_{ct}$ (K.m <sup>2</sup> /W)	1	2	Average
Without removable liners	0.116	0.113	0.115
With water-resistant liner	N/A	N/A	N/A

### Water spray and rain resistance

These pants have not been advertised as water-resistant so have not been tested for water spray and rain resistance.

#### Assessment Details.

Brand	PANDO MOTO
Model	SKIN UH AAA
Type	Pants(Undergarment) -Textile
Date purchased	4 December 2024
Tested by	AMCAF, Deakin University
Report approved by	MotoCAP Chief Scientist
Garment test reference	P25T10
Rating first published	February 2025
Rating updated	18 June 2025